



НҮҮРСНИЙ ОВООЛГЫН ҮЗҮҮЛЭЛТ

№ ETT_SP_SSC



ISO 45001:2018



ISO 9001:2015



ISO 14001:2015



НҮҮРСНИЙ ОВООЛГЫН ЧАНАРЫН ДУНДАЖ ҮЗҮҮЛЭЛТ

| | | |
|--|---|---|
| <p>НИЙТ ЧИЙГ (ar)</p> <p>3.3%</p> <p>(-1.0; +1.5)</p> | <p>ҮНСЛЭГ (db)</p> <p>20.5%</p> <p>(-4.0; +4.0)</p> | <p>ДЭГДЭМХИЙ (daf)</p> <p>34.0%</p> <p>(-2; +1)</p> |
| <p>НИЙТ ХҮХЭР (db)</p> <p>1.1%</p> <p>(-0.5; +0.5)</p> | <p>БАРЬЦАЛДАХ ЧАНАР</p> <p>70.0</p> <p>(-10; +10.0)</p> | <p>НҮҮРСНИЙ ХЭМЖЭЭ</p> <p>1000.0</p> <p>МЯН.ТН</p> |

НҮҮРСНИЙ ОВООЛГЫН ШИНЖИЛГЭЭНИЙ ҮР ДҮН

ALS GROUP LLC
Mongol National Building, 2nd Floor
Chinggis Avenue, Khan-Uul District
Ulaanbaatar, Mongolia
Tel: +976 79 007667



CERTIFICATE OF ANALYSIS
231102, 110, 130, 140, 163, 173, 188, 211-TT

CLIENT: Erdenes Tavan Tolgoi JSC
ADDRESS: Finance Center, Jiggijavh-8
1st Khoroо, Chingeltei District
Ulaanbaatar, Mongolia
ATTN: BekhterP
PROJECT NO.: xxx
LAB. JOB NO.: 231102, 110, 130, 140, 163, 173, 188, 211-TT
NO. SAMPLES: 15
Notes/Comments: xxx

SAMPLES RECEIVED: 13/Sep/23
INSTRUCTIONS RECEIVED: 13/Sep/23
DATE OF REPORT: 14/Sep/23
STATUS OF REPORT: FINAL
ANALYSIS COMPLETE: 14/Sep/23
PREPARATION CODE: CRUSH-01, 02; MILL-01
ANALYSIS CODE: 1. COKING CGAL, CSN
TM, ASH, MOIS, VOL,
TSUL, CKN
APPROVED BY: Laboratory Manager

Quality Manager
Checked By: Chief Chemist

These test results are representative only of the sample received in the laboratory.

| LAB NO. | SAMPLE NO. | AS RECEIVED BASIS | | | | | | | | | | | | | | AIR DRIED BASIS | | | | | | | | | | | | | | DRY BASIS | | | | | | | | | | | | | | Crucible Swelling Number (CSN) | Coal Caking Index (CKIN) | |
|---------|-----------------|---------------------|-----------|------------------------|-------------------|----------------------|-----------------|-----------|------------------------|-------------------|----------------------|-----------|------------------------|-------------------|----------------------|-----------------|------------------------|-------------------|----------------------|-----------|------------------------|-------------------|----------------------|-----------|-----------|-----|-----|--|--|-----------|--|--|--|--|--|--|--|--|--|--|--|--|--|--------------------------------|--------------------------|--|
| | | Total Moisture (TM) | Ash (ASH) | Volatiles Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Moisture (MOIS) | Ash (ASH) | Volatiles Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Ash (ASH) | Volatiles Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Ash (ASH) | Volatiles Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Ash (ASH) | Volatiles Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | GB/T 5448 | GB/T 5447 | 5:1 | 3:3 | | | | | | | | | | | | | | | | | | | |
| 1 | ETT_SP_20012-1A | 2.67 | 15.25 | 28.31 | 53.77 | 0.75 | 0.73 | 15.55 | 28.87 | 54.84 | 0.77 | 15.67 | 29.09 | 55.24 | 0.77 | 34.49 | 65.51 | 0.92 | 6.0 | 76 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 2 | ETT_SP_20012-1B | 2.26 | 13.23 | 28.78 | 55.73 | 0.67 | 0.71 | 13.44 | 29.24 | 56.62 | 0.68 | 13.54 | 29.44 | 57.02 | 0.69 | 34.05 | 65.95 | 0.79 | 6.5 | 79 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 3 | ETT_SP_20012-1C | 2.30 | 13.60 | 28.48 | 55.42 | 0.77 | 0.65 | 14.03 | 28.96 | 56.36 | 0.78 | 14.12 | 29.15 | 56.72 | 0.79 | 33.95 | 66.05 | 0.92 | 6.5 | 77 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 4 | ETT_SP_20012-2A | 6.22 | 15.24 | 26.54 | 52.00 | 0.96 | 1.04 | 14.08 | 28.01 | 54.87 | 1.01 | 16.29 | 28.30 | 55.45 | 1.02 | 33.99 | 66.21 | 1.22 | 5.0 | 63 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 5 | ETT_SP_20012-2B | 5.04 | 15.96 | 27.77 | 51.23 | 1.40 | 0.98 | 16.65 | 28.95 | 53.42 | 1.46 | 16.81 | 29.24 | 53.95 | 1.48 | 35.15 | 64.85 | 1.77 | 6.0 | 71 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 6 | ETT_SP_20012-2C | 4.13 | 13.47 | 27.78 | 54.61 | 0.94 | 0.95 | 13.92 | 28.71 | 56.42 | 0.97 | 14.06 | 28.98 | 56.96 | 0.98 | 33.72 | 66.28 | 1.14 | 5.5 | 67 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 7 | ETT_SP_20012-3A | 4.01 | 11.74 | 27.90 | 54.35 | 0.73 | 0.87 | 12.13 | 28.81 | 58.19 | 0.75 | 12.23 | 29.06 | 58.70 | 0.76 | 33.12 | 66.88 | 0.87 | 4.0 | 72 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 8 | ETT_SP_20012-3B | 3.98 | 13.91 | 26.57 | 55.54 | 0.84 | 0.91 | 14.36 | 27.42 | 57.31 | 0.86 | 14.49 | 27.67 | 57.84 | 0.87 | 32.36 | 67.44 | 1.02 | 5.0 | 65 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 9 | ETT_SP_20012-3C | 4.15 | 11.86 | 27.45 | 56.53 | 0.73 | 0.93 | 12.26 | 28.37 | 58.43 | 0.76 | 12.38 | 28.64 | 58.98 | 0.76 | 32.69 | 67.31 | 0.87 | 5.5 | 68 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 10 | ETT_SP_20012-4A | 3.23 | 13.88 | 26.84 | 56.05 | 1.05 | 0.78 | 14.23 | 27.52 | 57.47 | 1.07 | 14.34 | 27.74 | 57.92 | 1.08 | 32.38 | 67.62 | 1.26 | 6.0 | 70 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 11 | ETT_SP_20012-4B | 3.21 | 13.33 | 27.83 | 55.44 | 0.90 | 0.76 | 13.66 | 28.53 | 57.05 | 0.92 | 13.77 | 28.75 | 57.48 | 0.93 | 33.34 | 66.66 | 1.08 | 6.0 | 74 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 12 | ETT_SP_20012-4C | 3.24 | 18.92 | 25.82 | 52.01 | 1.05 | 0.81 | 19.40 | 26.48 | 53.32 | 1.08 | 19.56 | 26.69 | 53.75 | 1.09 | 33.18 | 66.82 | 1.35 | 3.5 | 49 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 13 | ETT_SP_20012-5A | 2.93 | 14.31 | 28.69 | 54.08 | 0.80 | 0.75 | 14.63 | 29.34 | 55.28 | 0.82 | 14.75 | 29.56 | 55.70 | 0.82 | 34.67 | 65.33 | 0.73 | 6.0 | 72 | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | | |
| 14 | ETT_SP_20012-5B | 2.35 | 15.48 | 28.18 | 53.02 | 0.51 | 0.79 | 15.89 | 28.91 | 54.42 | 0.52 | 16.01 | 29.14 | 54.85 | 0.53 | 34.69 | 65.21 | 0.83 | 6.0 | 89 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |
| 15 | ETT_SP_20012-5C | 4.22 | 14.26 | 28.42 | 52.90 | 0.59 | 0.79 | 14.77 | 29.65 | 54.80 | 0.61 | 14.89 | 29.88 | 55.23 | 0.61 | 35.11 | 64.89 | 0.72 | 6.0 | 78 | - | - | - | - | - | - | - | | | | | | | | | | | | | | | | | | | |

QUALITY ASSURANCE/QUALITY CONTROL DATA

| STDALYS-30/21 | ASH | VOL | TSUL |
|--------------------|-------|-------|--------|
| Control Value | 15.79 | 28.33 | 54.88 |
| Standard Deviation | 0.059 | 0.204 | 0.0136 |
| Unit | % | % | % |
| Analyzed value | 10.68 | 20.37 | 0.607 |

This is the Final Report and supersedes any preliminary report with the certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release. COPY RIGHT PROTECTED DOCUMENT

ALS GROUP LLC
Mongol National Building, 2nd floor
Chinggis Avenue, Khan-Uul District
Ulaanbaatar, Mongolia
Tel +976 70 007667



CERTIFICATE OF ANALYSIS
23E07; 23E108; 23E115; 23E135; 23F74; 23F145; 23J252-TT

CLIENT: Erdenes Tavan Tolgoi JSC
ADDRESS: Finance Center, Jigjidjav-8
1st khoroo, Chingelal District
Ulaanbaatar, Mongolia
ATTN: Galtzaya.B
PROJECT NO. xxx
LAB. JOB NO. 23E07; 23E108; 23E115; 23E135; 23F74; 23F145; 23J252-TT
NO. SAMPLES: 16
Notes/Comments: xxx

SAMPLES RECEIVED: 2023/05/02/2023/10/31
INSTRUCTIONS RECEIVED: 2023/05/02/2023/10/31
DATE OF REPORT: 2023/05/03/2023/10/31
STATUS OF REPORT: FINAL
ANALYSIS COMPLETE: 2023/05/03/2023/10/31
PREPARATION CODE: CRUSH-01_02_MLL-01
ANALYSIS CODE: 1_1_COKING COAL
TM, ASH, MOIS, VOL,
TSUL, CBR, CKN
APPROVED BY: Laboratory Manager
Quality Manager
CHECKED BY: Chief Chemist

These test results are representative only of the sample received in the laboratory.

| LAB NO. | SAMPLE NO. | AS RECEIVED BASIS | | | | AIR DRIED BASIS | | | | DRY BASIS | | | | DRY, ASH-FREE BASIS | | | | Crumble Swelling Number (CSN) | Coal Caking Index (CKI) | | |
|---------|------------------|---------------------|-----------|-----------------------|-------------------|----------------------|-----------------|-----------|-----------------------|-------------------|----------------------|-----------|-----------------------|---------------------|----------------------|-----------|-----------------------|-------------------------------|-------------------------|----------------------|-----|
| | | Total Moisture (TM) | Ash (ASH) | Volatile Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Moisture (MOIS) | Ash (ASH) | Volatile Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Ash (ASH) | Volatile Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Ash (ASH) | Volatile Matter (VOL) | | Fixed Carbon (FC) | Total Sulphur (TSUL) | 5:1 |
| 1 | ETT_SP_20009-1A | 1.64 | 17.74 | 27.09 | 53.53 | 1.04 | 0.50 | 17.95 | 27.40 | 54.15 | 1.05 | 18.04 | 27.54 | 54.43 | 1.06 | 33.60 | 66.40 | 1.20 | 6.0 | 7.0 | - |
| 2 | ETT_SP_20009-1B | 2.03 | 18.43 | 25.74 | 53.80 | 1.58 | 0.38 | 18.74 | 26.17 | 54.71 | 1.61 | 18.81 | 26.27 | 54.92 | 1.62 | 32.36 | 67.64 | 1.99 | 6.0 | 6.0 | - |
| 3 | ETT_SP_20009-1C | 7.06 | 17.20 | 25.57 | 50.18 | 1.55 | 1.13 | 18.29 | 27.20 | 53.37 | 1.65 | 18.50 | 27.51 | 53.99 | 1.67 | 33.76 | 66.24 | 2.04 | 5.8 | - | - |
| 4 | ETT_SP_20009-1D | 2.82 | 15.94 | 27.88 | 53.39 | 0.75 | 0.87 | 15.26 | 28.42 | 54.46 | 0.77 | 15.40 | 28.66 | 54.98 | 0.77 | 34.29 | 65.71 | 0.93 | 7.7 | - | - |
| 5 | ETT_SP_20009-1E | 2.43 | 16.85 | 27.40 | 53.33 | 0.75 | 0.94 | 17.11 | 27.81 | 54.14 | 0.76 | 17.27 | 28.08 | 54.65 | 0.77 | 33.94 | 66.06 | 0.93 | 7.7 | - | - |
| 6 | ETT_SP_20009-1F | 2.47 | 15.44 | 25.99 | 53.10 | 0.61 | 0.92 | 15.69 | 27.42 | 55.98 | 0.62 | 15.83 | 27.67 | 56.50 | 0.62 | 32.88 | 67.12 | 0.74 | 7.2 | - | - |
| 7 | ETT_SP_20009-1G | 2.34 | 15.68 | 27.03 | 54.95 | 0.71 | 0.88 | 15.91 | 27.44 | 55.77 | 0.72 | 16.05 | 27.88 | 56.27 | 0.72 | 32.97 | 67.03 | 0.86 | 7.0 | - | - |
| 8 | ETT_SP_20009-2A | 4.47 | 17.10 | 25.21 | 53.23 | 0.62 | 0.79 | 17.76 | 26.18 | 55.68 | 0.65 | 17.98 | 26.39 | 55.72 | 0.65 | 32.14 | 67.86 | 0.79 | 6.0 | 7.5 | - |
| 9 | ETT_SP_20009-2B | 4.83 | 13.79 | 26.94 | 54.44 | 0.40 | 0.97 | 14.35 | 28.03 | 56.65 | 0.42 | 14.49 | 28.30 | 57.21 | 0.42 | 33.10 | 66.90 | 0.49 | 5.5 | 6.4 | - |
| 10 | ETT_SP_20009-2C | 1.04 | 16.76 | 27.70 | 54.50 | 0.53 | 0.58 | 16.84 | 27.83 | 54.75 | 0.53 | 16.93 | 27.99 | 55.07 | 0.54 | 33.70 | 66.30 | 0.65 | 6.2 | - | - |
| 11 | ETT_SP_20009-W2A | 3.67 | 18.64 | 27.09 | 52.60 | 1.11 | 0.66 | 17.16 | 27.98 | 54.25 | 1.14 | 17.27 | 28.12 | 54.60 | 1.15 | 33.99 | 66.01 | 1.39 | 6.3 | - | - |
| 12 | ETT_SP_20009-W2B | 2.64 | 18.12 | 27.03 | 52.21 | 0.73 | 0.98 | 18.43 | 27.50 | 53.10 | 0.74 | 18.61 | 27.77 | 53.63 | 0.75 | 34.11 | 65.89 | 0.92 | 5.0 | 5.8 | - |
| 13 | ETT_SP_20009-W2C | 1.98 | 20.37 | 28.27 | 51.41 | 0.74 | 0.67 | 20.53 | 26.61 | 52.08 | 0.75 | 20.77 | 26.79 | 52.44 | 0.75 | 33.82 | 66.18 | 0.95 | 5.0 | 5.6 | - |
| 14 | ETT_SP_20009-E3A | 2.78 | 18.01 | 28.44 | 52.78 | 0.85 | 0.69 | 18.35 | 27.05 | 53.91 | 0.84 | 18.46 | 27.25 | 54.29 | 0.87 | 35.01 | 64.99 | 1.04 | 6.0 | 7.1 | - |
| 15 | ETT_SP_20009-E3B | 1.95 | 19.02 | 28.00 | 51.03 | 0.89 | 0.57 | 19.29 | 28.39 | 51.75 | 0.90 | 19.40 | 28.55 | 52.04 | 0.91 | 35.43 | 64.57 | 1.13 | 5.5 | 6.4 | - |
| 16 | ETT_SP_20009-E3C | 2.18 | 18.99 | 27.14 | 51.69 | 0.78 | 0.60 | 19.30 | 27.58 | 52.52 | 0.80 | 19.42 | 27.75 | 52.84 | 0.80 | 34.43 | 65.57 | 1.00 | 5.0 | 5.5 | - |

QUALITY ASSURANCE/QUALITY CONTROL DATA

| STDALSIWS-23/20 | ASH | VOL | TSUL |
|--------------------|-------|-------|-------|
| Certified Value | 18.25 | 18.18 | 0.616 |
| Standard Deviation | 0.63 | 0.16 | 0.017 |
| Unit | % | % | % |
| Analyzed value | 18.86 | 18.22 | 0.615 |

This is the Final Report and is supersede any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release. COPY RIGHT PROTECTED DOCUMENT

Page 1 of 1

ALS GROUP LLC
Mongol National Building, 2nd floor
Chinggis Avenue, Khan-Uul District
Ulaanbaatar, Mongolia
Tel +976 70 007667



CERTIFICATE OF ANALYSIS
23J194; 23J210; 23J236; 23J242; 23K04-TT

CLIENT: Erdenes Tavan Tolgoi JSC
ADDRESS: Finance Center, Jigjidjav-8
1st khoroo, Chingelal District
Ulaanbaatar, Mongolia
ATTN: Bekhtur.P
PROJECT NO. xxx
LAB. JOB NO. 23J194; 23J210; 23J236; 23J242; 23K04-TT
NO. SAMPLES: 9
Notes/Comments: xxx

SAMPLES RECEIVED: 01/11-24/10/2023
INSTRUCTIONS RECEIVED: 01/11-24/10/2023
DATE OF REPORT: 02/11-25/10/2023
STATUS OF REPORT: FINAL
ANALYSIS COMPLETE: 02/11-25/10/2023
PREPARATION CODE: CRUSH-01_02_MLL-01
ANALYSIS CODE: 1_COKING COAL, CBN
TM, ASH, MOIS, VOL,
TSUL, CKN
APPROVED BY: Laboratory Manager
Quality Manager
CHECKED BY: Chief Chemist

These test results are representative only of the sample received in the laboratory.


| LAB NO. | SAMPLE NO. | AS RECEIVED BASIS | | | | AIR DRIED BASIS | | | | DRY BASIS | | | | DRY, ASH-FREE BASIS | | | | Crumble Swelling Number (CSN) | Coal Caking Index (CKI) | | |
|---------|-----------------|---------------------|-----------|-----------------------|-------------------|----------------------|-----------------|-----------|-----------------------|-------------------|----------------------|-----------|-----------------------|---------------------|----------------------|-----------|-----------------------|-------------------------------|-------------------------|----------------------|-----|
| | | Total Moisture (TM) | Ash (ASH) | Volatile Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Moisture (MOIS) | Ash (ASH) | Volatile Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Ash (ASH) | Volatile Matter (VOL) | Fixed Carbon (FC) | Total Sulphur (TSUL) | Ash (ASH) | Volatile Matter (VOL) | | Fixed Carbon (FC) | Total Sulphur (TSUL) | 5:1 |
| 1 | ETT_SP_20017-1A | 2.33 | 16.68 | 27.71 | 53.28 | 0.96 | 0.64 | 16.96 | 28.19 | 54.20 | 0.97 | 17.07 | 28.38 | 54.55 | 0.98 | 34.22 | 65.78 | 1.18 | 6.0 | 7.4 | - |
| 2 | ETT_SP_20017-1B | 2.37 | 15.81 | 28.70 | 53.12 | 1.02 | 0.64 | 16.09 | 29.21 | 54.06 | 1.04 | 16.19 | 29.40 | 54.41 | 1.04 | 35.08 | 64.92 | 1.25 | 6.0 | 7.2 | - |
| 3 | ETT_20017_1C-1 | 2.34 | 15.98 | 27.00 | 54.48 | 0.96 | 0.63 | 16.26 | 27.48 | 55.63 | 0.99 | 16.36 | 27.65 | 55.99 | 1.00 | 32.06 | 66.94 | 1.19 | 6.7 | - | - |
| 4 | ETT_SP_20017-2A | 3.19 | 14.09 | 28.63 | 54.09 | 0.91 | 0.51 | 14.48 | 29.42 | 55.59 | 0.93 | 14.56 | 29.57 | 55.87 | 0.94 | 34.61 | 65.39 | 1.10 | 6.5 | 7.7 | - |
| 5 | ETT_SP_20017-2B | 3.48 | 12.98 | 29.17 | 54.28 | 0.75 | 0.72 | 13.35 | 30.00 | 55.93 | 0.77 | 13.45 | 30.22 | 56.33 | 0.77 | 34.91 | 65.09 | 0.89 | 6.5 | 8.1 | - |
| 6 | ETT_SP_20017-2C | 2.89 | 15.17 | 27.62 | 54.01 | 0.76 | 0.70 | 15.51 | 28.58 | 55.23 | 0.80 | 15.62 | 28.76 | 55.62 | 0.80 | 34.08 | 65.92 | 0.95 | 5.5 | 7.2 | - |
| 7 | ETT_SP_20017-3A | 3.06 | 12.57 | 29.27 | 55.10 | 0.59 | 1.03 | 12.83 | 29.98 | 54.25 | 0.60 | 12.97 | 30.20 | 54.84 | 0.60 | 34.69 | 65.31 | 0.69 | 6.5 | 8.2 | - |
| 8 | ETT_SP_20017-3B | 3.43 | 13.19 | 29.08 | 54.30 | 0.61 | 1.00 | 13.52 | 29.81 | 55.67 | 0.63 | 13.65 | 30.11 | 56.23 | 0.63 | 34.87 | 65.13 | 0.73 | 6.5 | 8.2 | - |
| 9 | ETT_SP_20017-3C | 3.54 | 12.25 | 29.12 | 55.09 | 0.55 | 1.10 | 12.56 | 29.86 | 56.49 | 0.57 | 12.70 | 30.19 | 57.11 | 0.57 | 34.58 | 65.42 | 0.66 | 6.5 | 8.1 | - |

QUALITY ASSURANCE/QUALITY CONTROL DATA

| STDALSIWS-010-2022 | ASH | VOL | TSUL |
|--------------------|-------|-------|-------|
| Certified Value | 18.46 | 17.79 | 0.666 |
| Standard Deviation | 0.079 | 0.127 | 0.015 |
| Unit | % | % | % |
| Analyzed value | 16.43 | 19.81 | 0.613 |

This is the Final Report and is supersede any preliminary report with this certificate number. Results apply to samples as submitted. All pages of this report have been checked and approved for release. COPY RIGHT PROTECTED DOCUMENT

Page 1 of 1

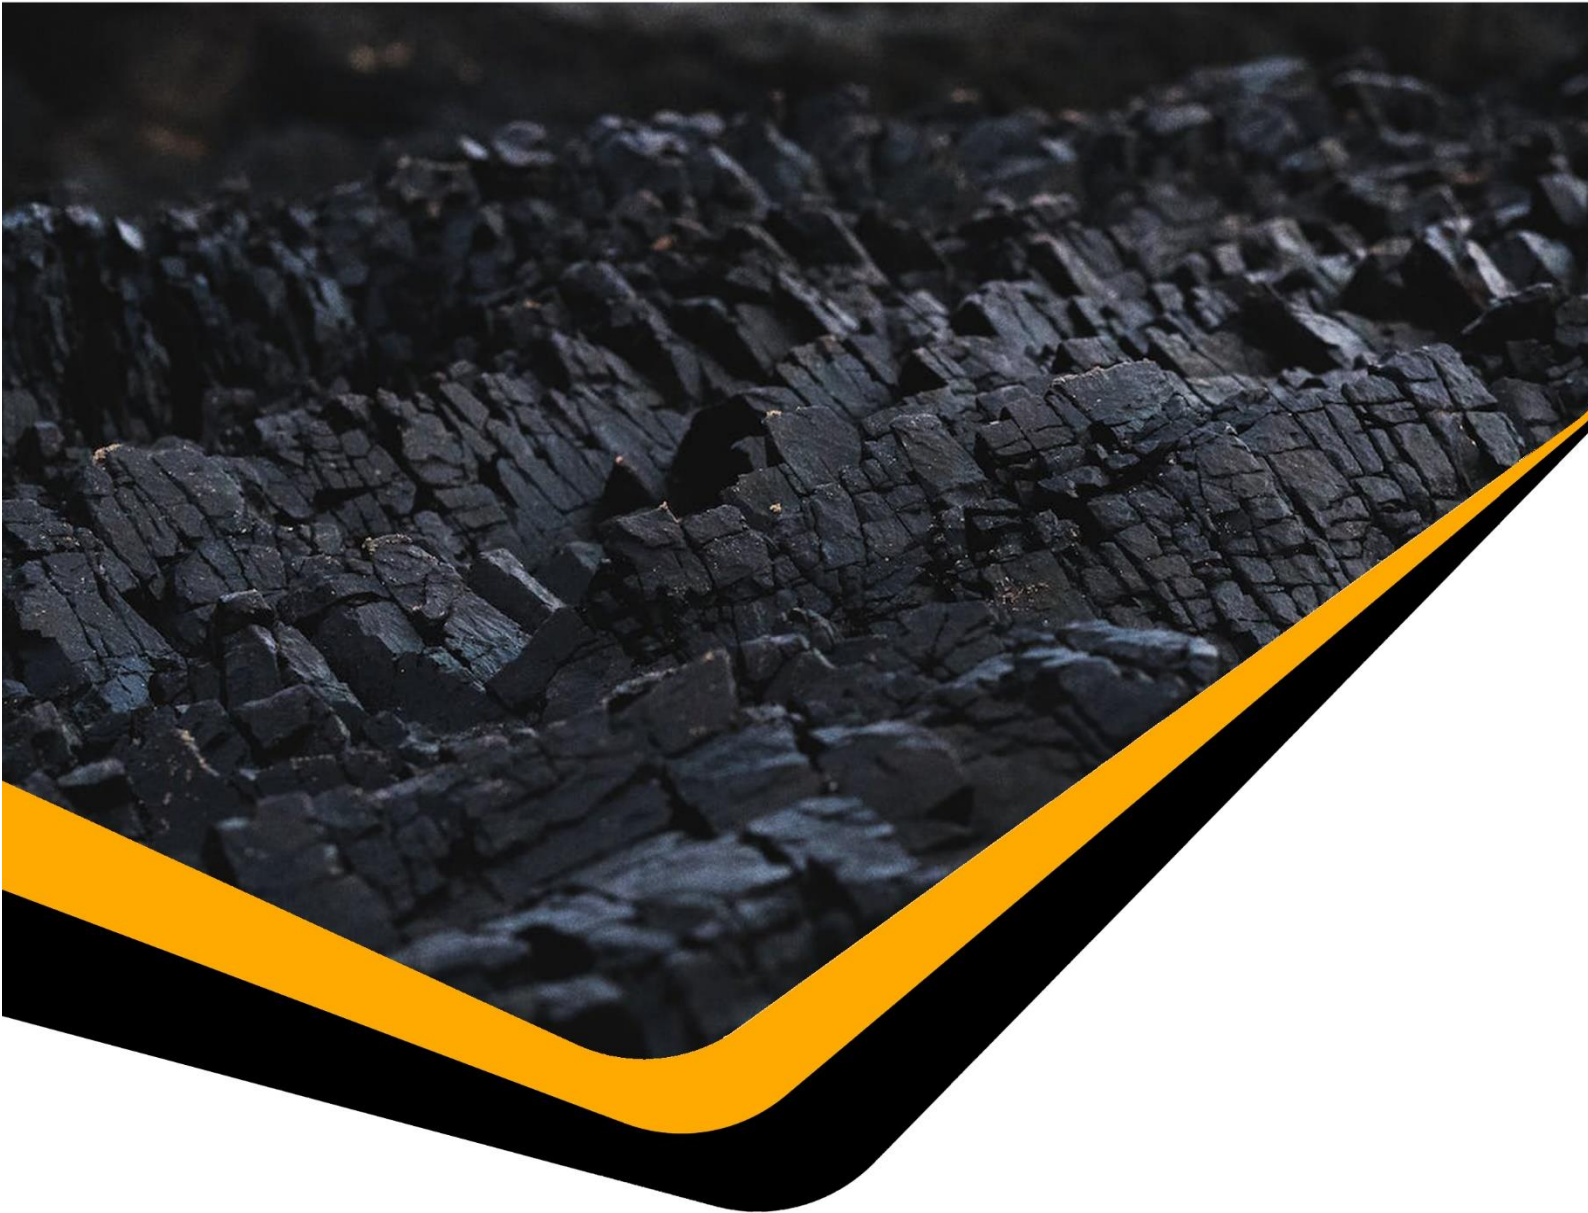

ISO 45001:2018



ISO 9001:2015



ISO 14001:2015



www.ett.mn



75055555
1800-1072



Финанс төв, 1-р хороо,
Чингэлтэй дүүрэг,
Улаанбаатар хот

